

TUNABLE HIGH GRADIENT QUADRUPOLES FOR A LASER PLASMA ACCELERATION BASED FEL*

A. Ghaith[†], F. Marteau, P. N'gotta, M. Valléau, J. Veteran, F. Blache, C. Kitegi,
 M. E. Couprise, Synchrotron SOLEIL, Gif-sur-Yvette, France
 C. Benabderrahmane, ESRF, 71 Avenue des martyrs, Grenoble 38000, France.
 O. Cosson, F. Forest, P. Jivkov, J. L. Lancelot,
 SigmaPhi, Rue des Freres Montgolfier, 56000 Vannes, France

Abstract

The magnetic design and characterization of tunable high gradient permanent magnet based quadrupole, or so-called QUAPEVAs, are presented. To achieve a high gradient field with a compact structure, permanent magnets are chosen rather than usual electro-magnets due to their small aperture. The quadrupole structure consists of two quadrupoles superimposed capable of generating a gradient of 210 T/m. The first quadrupole is composed of permanent magnets following a Halbach configuration shaped as a ring attaining a constant gradient of 160 T/m, and the second of four permanent magnet cylinders surrounding the ring and capable of rotating around their axis to achieve a gradient tunability of ± 50 T/m. Each tuning magnet is connected to a motor and is controlled independently, enabling the gradient to be tuned with a rather good magnetic center stability ($20 \mu\text{m}$ and without any field asymmetry). Seven quadrupoles have been built with different magnetic lengths in order to fulfil the integrated gradient required. A set of QUAPEVA triplet are now in use, to focus a high divergent electron beam with large energy spread generated by a laser plasma acceleration source for a free electron laser application [?].

INTRODUCTION

Accelerator physics and technology have recently seen tremendous developments especially in synchrotron radiation domain, which is actively investigating low emittance storage rings with multibend achromat optics for getting closer to the diffraction limit and providing a high degree of transverse coherence [1]. In addition, Laser Plasma Acceleration (LPA) can now generate a GeV beam within a very short accelerating distance, with high peak current ~ 10 kA, but the high divergence (few mrad) and large energy spread (few percent) have to be handled.

All these recent developments require high gradient quadrupoles that can not be provided by usual room temperature electron-magnet technology. To achieve a high gradient, one is more likely to choose either superconducting or permanent magnet [2] technologies. Permanent Magnets (PMs) can be arranged in the so-called Halbach configuration [3], to provide a quadrupolar field. Permanent magnet quadrupoles knew recently a renewed interest, because of their compactness and their capacity of reaching high field

gradient, alongside the absence of power supplies, letting them to be a solution for future sustainable green society.

DESIGN

The QUAPEVA is composed of two superimposed quadrupoles, one placed at the center following a Halbach configuration, surrounded by another that consists of four rotating cylindrical magnets to provide the gradient variability (see Fig.1). Fig. 1 also shows three particular configurations of the tuning magnets; (a) maximum gradient: tuning magnets easy axis towards the central magnetic poles, (b) intermediate gradient: the tuning magnets are in the reference position, i.e. their easy axis is perpendicular to the central magnetic poles, (c) minimum gradient: tuning magnets easy axis away from the central magnetic poles. Table. 1 shows the QUAPEVA parameters alongside the characteristics of the magnets and poles.

Table 1: QUAPEVA parameters. GFR is good field region.

Parameters	Value	Unit
Gradient (G)	110 - 210	T/m
Remanent Field (B_r)	1.26	T
Coercivity (H_{cj})	1830	kA/m
GFR	4	mm
$\Delta G/G$	< 0.01	at 4 mm

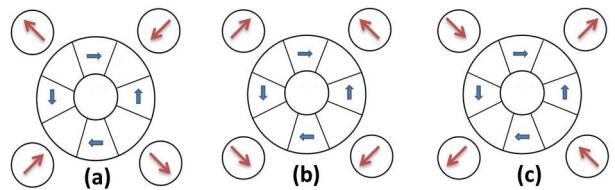


Figure 1: (a) maximum gradient, (b) intermediate gradient, (c) minimum gradient.

In order to optimize the geometry and magnetic parameters, QUAPEVAs are modeled using two numerical tools: RADIA [4] a magnetostatic code based on boundary integral method where materials are meshed; TOSCA [5] a finite element magnetostatic code.

Fig. 2 shows the gradient computed as the cylindrical magnets rotate in the case of the 100 mm magnetic length system. The intermediate gradient is ~ 160 T/m, and due

* Synchrotron SOLEIL

[†] amin.ghaith@synchrotron-soleil.fr

to the rotating magnets it can be increased by $\sim 50\%$ up to 210 T/m.

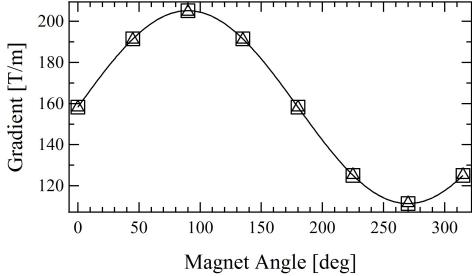


Figure 2: Gradient computed as the cylindrical magnets are rotating for the 100 mm magnetic length QUAPEVA. (□) RADIA, (△) TOSCA.

The motors have sufficient torque to counteract the magnetic forces induced by the magnetic system, are very compact ($48.5 \times 50 \times 50 \text{ mm}^3$), and have an encoder within a $31 \mu\text{rad}$ resolution. The magnetic system is mounted on an Aluminum frame and the motors are placed at the four corners of the frame to avoid perturbations of the magnetic field as shown in Fig. 3. A non-magnetic belt transmits the rotation movement from the motor to the cylindrical magnets. Each magnet is connected to one motor to allow for a precise positioning of each magnet and minimizes the magnetic center shift at different gradients. The quadrupole is mounted on a translation table (horizontal and vertical displacement) used to compensate any residual magnetic axis shift when varying the gradient, to perform electron beam based alignment or for the magnetic measurements benches.

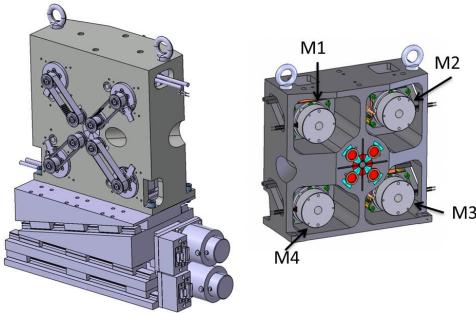


Figure 3: QUAPEVA design mounted on a translation table.

MAGNETIC MEASUREMENTS

A dedicated radial rotating coil (see Fig. 4) of 10 mm diameter was built for the SOLEIL magnet characterization bench [8], to fit the quadrupole inner diameter of 10.5 mm. In order to qualify the accuracy of the rotating coil, a permanent magnet quadrupole with a 76 mm diameter bore has been measured first with a reference coil and then with the 10 mm diameter coil. The geometrical parameter of the new coil has been determined in order to find the same harmonic content with both coils at 4 mm.



Figure 4: Rotating coil bench installed at SOLEIL.

The integrated gradient of the seven systems with different magnetic lengths is measured and compared to the simulations of RADIA and TOSCA in Fig. 5. They show good agreement with a difference no larger than 4%.

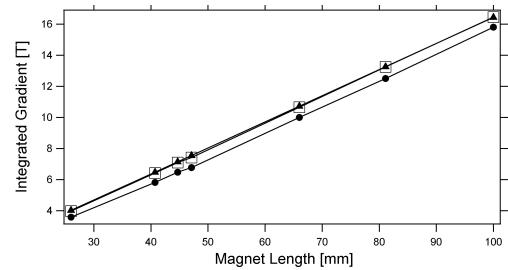


Figure 5: Integrated gradient of the seven systems for the intermediate gradient case. (□) RADIA, (△) TOSCA, (●) rotating coil.

The stretch-wire bench developed at ESRF [9] has been used for magnetic field integral measurements (see Fig. 6). The wire is positioned inside the magnet gap and its resonance frequency is tuned. Its sag depends on its tension. A voltage proportional to the variation of magnetic flux is induced and measured with a Keithley nanovoltmeter, resulting in the first field integral. A granite table supports the linear stages and the measured magnet. The stretched wire bench enables to perform fast measurement at a good precision with good repeatability.

This method has been used to calculate the magnetic center excursion as the gradient is varied. The center stability is found to be within $\pm 10 \mu\text{m}$.

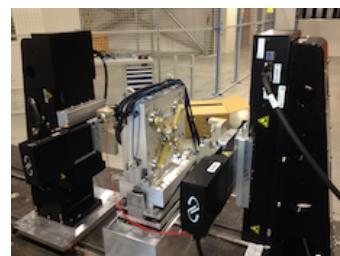


Figure 6: Stretched wire bench at ESRF.

The pulsed-wire method has been used to align the magnetic center of the three QUAPEVAs (see Fig. 7) before their installation at COXINEL transport line [7]. It is based on applying a square current pulse through a wire placed in a magnetic field, which induces an interaction due to

Lorentz force. This force leads to wire displacement which is measured using a motion laser detector [10].



Figure 7: Pulsed wire system setup with three QUAPEVAs (26 mm, 40.7 mm, and 44.7 mm mechanical lengths).

A first triplet of QUAPEVA was checked with the pulsed wire technique in view of the COXINEL application. The three QUAPEVA were directly installed on the bench, with a medium gradient value setting and with random values for the horizontal and vertical positions of the translation stage. The pulse wire measurements for such a deviation show deviations of the magnetic axis from the axis. Then, the three QUAPEVA were centered one by one, starting from the 40.7 mm, then the 44 mm and finally the 26 mm. Such an adjustment had been performed with only two iterations for each quadrupole : The first measurement is performed for the actual position and the second one while the it has been moved from $250 \mu\text{m}$ in vertical and horizontal. As the field is proportional to the displacement, the new positions to apply are calculated from these two measurements to recover the center. This pulse wire technique was thus used for checking the final alignment and the absence of cross talk between the magnets.

COXINEL

A first triplet (26 mm, 40.7 mm, 44.7 mm mechanical length) is used for focusing the electron beam produced by laser plasma acceleration at Laboratoire d'Optique Appliquée in view of electron qualification with a Free Electron Laser application. The results from the pulsed wire measurement have been used for QUAPEVA alignment during COXINEL experiment. Fig. 8 shows the electron beam, using a lanex screen placed 3 m away from the electron source, without and with the triplet. The large divergent beam is well focused.

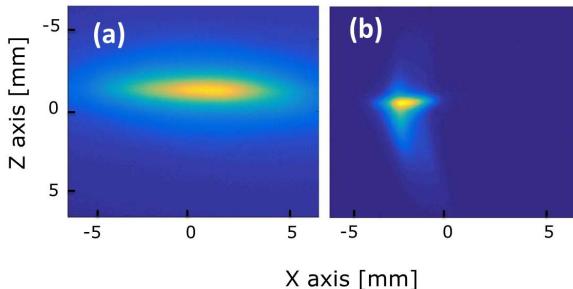


Figure 8: (a) without QUAPEVAs, (b) with QUAPEVAs.

CONCLUSION

The design and magnetic measurements of a permanent magnet based quadrupoles of variable strength have been presented. A high gradient ($\sim 210 \text{ T/m}$) with a wide tuning range ($\sim 100 \text{ T/m}$) is obtained with such a design. The measurement using different methods are consistent and in good agreement between themselves and the simulations. The quadrupoles have been installed successively at COXINEL beam line, and are able to achieve good focusing with a highly divergent large energy spread beam.

ACKNOWLEDGEMENT

The authors are very grateful to the European Research Council for the advanced grant COXINEL (340015) and also to the Fondation de la Coopération Scientifique for the Triangle de la Physique / valorisation contract QUAPEVA (2012-058T). The authors are very thankful for the COXINEL team. The authors also acknowledge the Laboratoire d'Optique Appliquée team led by V. Malka for the generation of the electron beam by laser plasma acceleration, enabling to use the QUAPEVA.

REFERENCES

- [1] Yunhai Cai, Karl Bane, Robert Hettel, Yuri Nosochkov, Min-Huey Wang, and Michael Borland. *Physical Review Special Topics-Accelerators and Beams*, 15(5):054002, 2012.
- [2] M. E. Couplie, A. Loulergue, M. Labat, R. Lehe, and Victor Malka. *Journal of Physics B: Atomic, Molecular and Optical Physics*, 47(23):234001, 2014.
- [3] K. Halbach, “Physical and optical properties of rare earth cobalt magnets,” *Nuclear Instruments and Methods in Physics Research*, vol. 187, no. 1, pp. 109–117, 1981.
- [4] K. Halbach, “Conceptual design of a permanent quadrupole magnet with adjustable strength,” *Nuclear Instruments and Methods in Physics Research*, vol. 206, no. 3, pp. 353–354, 1983.
- [5] O. Chubar, P. Elleaume, and J. Chavanne, “A three-dimensional magnetostatics computer code for insertion devices,” *Journal of Synchrotron Radiation*, vol. 5, no. 3, pp. 481–484, 1998.
- [6] J. Simkin and C. Trowbridge, “Three-dimensional nonlinear electromagnetic field computations, using scalar potentials,” in *IEE Proceedings B-Electric Power Applications*, vol. 127, pp. 368–374, IET, 1980.
- [7] C. Benabderrahmane, M. Couplie, F. Forest, and O. Cosson, “Adjustable magnetic multipole,” 2016. Europe : PCT/EP2015/069649 of 27/08/2015, WOBL14SSOQUA / CA.
- [8] M. Couplie, M. Labat, C. Evain, F. Marteau, F. Briquet, M. Khojyan, C. Benabderrahmane, L. Chapuis, N. Hubert, C. Bourassin-Bouchet, et al., “An application of laser-plasma acceleration: towards a free-electron laser amplification,” *Plasma Physics and Controlled Fusion*, vol. 58, no. 3, p. 034020, 2016.
- [9] A. Madur, *Contribution à la métrologie magnétique des multipoles d'accélérateurs: les quadrupôles du Synchrotron SOLEIL*. PhD thesis, Vandoeuvre-les-Nancy, INPL, 2006.

- [10] G. Le Bec, J. Chavanne, and C. Penel, “Stretched wire measurement of multipole accelerator magnets,” *Physical Review Special Topics-Accelerators and Beams*, vol. 15, no. 2, p. 022401, 2012.
- [11] D. W. Preston and R. W. Warren, “Wiggler field measurements and corrections using the pulsed wire technique,” *Nu-*
clear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment, vol. 318, no. 1-3, pp. 794–797, 1992.